

Chiral hidden order and orbital antiferromagnetic fluctuations in URu₂Si₂

P. Kotetes,* A. Aperis, and G. Varelogiannis

Department of Physics, National Technical University of Athens, GR-15780 Athens, Greece

The heavy fermion compound URu₂Si₂ exhibits some of the most enigmatic manifestations of strongly correlated electronic matter. Cooling down to $T_o = 17.5\text{K}$, reorders its ground state via a second order phase transition to an unidentified exotic order, the so called ‘*hidden order*’ (HO), whose fingerprint is a large specific heat jump and a disproportionately small antiferromagnetic moment. Below 1.5K, the HO becomes superconducting, while it evolves to a large moment antiferromagnetic state (LMAF) upon raising pressure, through a first-order phase transition. A cascade of metamagnetic steps, an anomalous giant Nernst signal and a characteristic gapped spin excitation at $Q = (1, 0, 0)$, add more mystery to the HO’s identity. Here we provide for the first time, a unified understanding of the observed anomalous thermoelectricity, the unresolved metamagnetic behaviour and the existence of two distinct energy scales, demonstrating that the HO state is in fact a chiral $d_{xy} + id_{x^2-y^2}$ spin density wave state. The inelastic magnetic response at Q , is attributed to the emergence of a novel orbital antiferromagnetic collective mode, rotating the HO to the LMAF. Finally, we make specific predictions for a Polar Kerr experiment.

The ‘hidden’ order (HO) transition of URu₂Si₂ attracted enormous attention, due to the mismatch of its specific heat jump at $T_o=17.5\text{K}$ and the concomitant c-axis oriented tiny antiferromagnetic moment $0.03\mu_B/U$, of wave-vector $Q_0 = (0, 0, 1)^{1,2}$. This incompatibility has raised great controversy on whether the genuine spin-dipolar antiferromagnetic moment inferred from the Bragg reflection at Q_0^3 , may be the driving order parameter of this transition. In fact, NMR measurements have revealed that antiferromagnetism is inhomogeneous in the HO state and the small observed moment arises probably due to a reduced volume effect^{4,5}. In addition, experiments have found no evidence for higher spin-correlators⁶. These observations are strongly in favour of a multipolar order parameter scenario.

Inelastic neutron scattering (INS) measurements^{7–11}, have revealed two gapped spin excitations at the wave-vectors $Q = (1, 0, 0)$ (equivalent to Q_0) and $Q_1 = (1 \pm 0.4, 0, 0)$. Specifically, the first resonance always accompanies the HO state and disappears in the LMAF^{10,11}, while the second persists and acquires a larger gap by effecting pressure. In the HO, the gap of the Q excitation, ω_Q^0 , increases upon raising the field, while the $\omega_{Q_1}^0$ slightly diminishes⁸. The latter implies the exis-

tence of two different energy scales, that none of them seems to fit to the energy gap dictating the thermodynamic properties of the HO¹². Moreover, the emergence of incommensurate excitations can be only understood within an itinerant picture⁹ that is also supported by the existence of strong Fermi surface nesting at Q_1 ¹³ and the recent verification of Fermi surface gapping in Angularly Resolved Photoemission Spectroscopy (ARPES) experiments¹⁴. In fact, the coincidence of the nesting vector with the momentum of the incommensurate spin excitation has been considered¹⁵ as the consequence of the creation of a spin exciton, due to the formation of a density wave state with ordering wave-vector Q_1 .

All the aforementioned properties point to the direction of a multipolar density wave state developed at the incommensurate vector Q_1 . The quadrupolar implementation of this scenario had been proposed earlier by Ramirez *et al*¹⁶, in order to account for the anomaly observed in the non-linear susceptibility. Nevertheless, a proposal of this type has to answer first of all the emergence of tremendously important characteristic phenomena that accompany the HO phase. These are the puzzling metamagnetism^{17,18} and giant Nernst signal^{19,20}, together with the existence of two different energy scales^{8,12}.

Here, we demonstrate that the hidden order that lurks in the $\mathcal{B} - T$ phase diagram of URu₂Si₂ is the incommensurate chiral $d_{xy} + id_{x^2-y^2}$ spin density wave state ordered at Q_1 . This state consists of a two component order parameter, with the second of them corresponding to the orbital antiferromagnetic orders proposed earlier for the HO^{21–23}. The additional d_{xy} component renders the HO *chiral* rather than *orbital*, violating time-reversal in a macroscopic level due to the development of an intrinsic ferromagnetic orbital moment. It has been shown, that due to this orbital magnetic-field-coupling, any unconventional density wave of the form $id_{x^2-y^2}$ will acquire an additional field-dependent d_{xy} component^{24,25}, *that could provide the missing energy scale*. Even if the chiral order does not appear in zero-field, it will be necessarily field-induced affecting the $\mathcal{B} - T$ phase diagram of the HO and every transport measurement realized in the presence of a field, such as the Nernst effect. Notice that associating the HO with a chiral state may be crucial for understanding the development of an unconventional superconducting state confined in the HO, that has been also considered to be chiral²⁶.

The proposed two-component chiral state may be viewed as the most general picture of an unconventional density wave order. In this sense, our theory is fully compatible with all the earlier proposed itinerant uncon-

ventional density wave models, and it could be considered as a natural extension to them. However, the chiral state exhibits properties not familiar to orbital orders. The violation of time-reversal symmetry leads to a Polar Kerr effect²⁷ and the generation of anomalous Hall electric²⁸ and thermoelectric currents^{29,30}, including the ‘tilted-hill’ giant Nernst signal recently shown to arise in strongly insulating chiral condensates³⁰. By adopting a simple microscopic model and an SO(2) invariant Ginzburg-Landau theory, we shall explain in a unified manner not only the metamagnetic behaviour and the anomalous thermoelectric transport but also the inelastic neutron scattering spectra.

Within a mean-field approximation, we have reproduced self-consistently the $\mathcal{B} - T$ phase diagram of this compound. For mediating the HO we have considered repulsive nearest and next-nearest inter-site Coulomb interactions of the form $\sum_{i \neq j} V_{ij} n_i n_j$. The order parameter field is described as a c-axis polarized spin-triplet order parameter $\Delta_{\mathbf{Q}_1}^z(\mathbf{k}) = \Delta_1 \sin k_x \sin k_y - i\Delta_2 (\cos k_x - \cos k_y)$, with ordering wave-vector $\mathbf{Q}_1$. For the metallic state of URu₂Si₂ we have considered a single-band nesting model described by the energy dispersion $\varepsilon(\mathbf{k}) = -2t(\cos k_x + \cos k_y)$. We have to remark that our results are independent of the microscopic details of the particular model.

The resulting $\mathcal{B} - T$ phase diagram is depicted in Fig.1a,b. We observe that our phase diagram grasps to a large extent both qualitative and quantitative features of the experimental observations^{17,18}. At $\mathcal{B} = 0\text{T}$, $\Delta_1 = 0$ and $\Delta_2 = 1.55\text{meV}$. The latter order parameter corresponds to the $id_{x^2-y^2}$ component that as we observe in Fig.1c, slightly decreases upon raising the magnetic field for low temperatures. In contrast, the d_{xy} order parameter Δ_1 , rises monotonically. We locate a Metamagnetic Critical End Point³¹ (MCEP) at $\mathcal{B}_{c1} = 33.5\text{T}$ and $T \simeq 3\text{K}$, down to which the driving HO gap, Δ_2 , evolves continuously with the magnetic field satisfying the quadratic relation $\Delta_2(\mathcal{B}_z)/\Delta_2(0) \simeq 1 - (\mathcal{B}_z/\mathcal{B}_{c1})^2$. This behaviour has been verified in magnetoresistance measurements¹². In stark contrast, Δ_2 remains practically constant for temperatures below the MCEP, giving rise to the field independent energy scale witnessed in the inelastic magnetic response at $\mathbf{Q}_1$ ⁸. A continuous evolution with the field is not compatible with the first-order character of the metamagnetic step. This property settles the controversy concerning the field dependence of the HO.

Our self-consistent phase diagram exhibits double-step metamagnetism (Fig.1d) at $\mathcal{B}_{c1} = 33.5\text{T}$ and $\mathcal{B}_{c2} \simeq 41\text{T}$, below 3K in agreement with experiments^{17,18}. Notice that the occurrence of metamagnetism in such a high field scale, is intimately related to the appearance of the d_{xy} component, leading to an enhancement of the critical temperature of the dominant $d_{x^2-y^2}$ order parameter. The gradual increment of the field, shifts the four quasi-particle bands through the combined orbital-Zeeman coupling. At each $\mathcal{B}_c$, an additional energy branch crosses the Fermi level (Fig.1e), providing an abrupt increase in

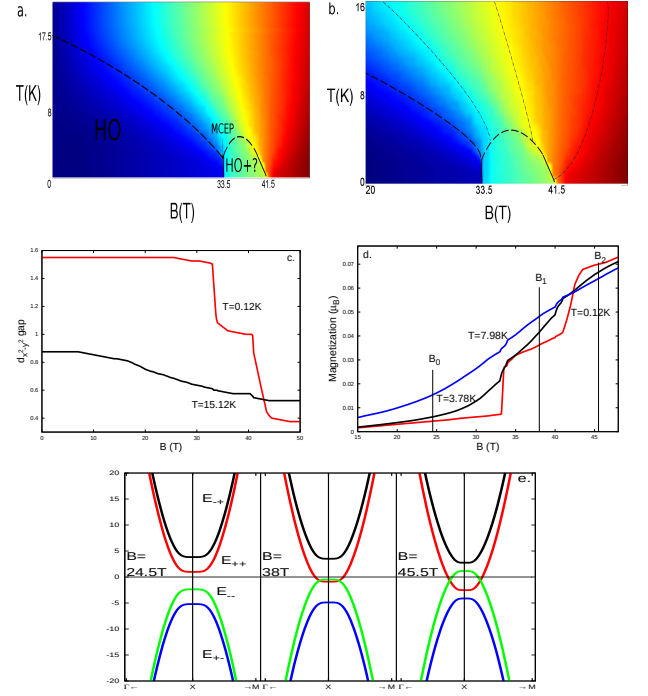


FIG. 1: a. Self-consistently extracted $\mathcal{B} - T$ phase diagram of the chiral d-spin density wave. The chiral HO is present everywhere in this phase diagram. The reduced magnitude of the order parameters in the high field and temperature regions, mask its presence providing a thermodynamic phase boundary (dashed lines). b. A Metamagnetic Critical End Point (MCEP) is located at $T \simeq 3\text{K}$ and $\mathcal{B} = \mathcal{B}_{c1} = 33.5\text{T}$. Two metamagnetic steps appear at $\mathcal{B}_{c1} = 33.5\text{T}$ and $\mathcal{B}_{c2} \simeq 41\text{T}$ along with the formation of crossover areas (separated by dash-dotted lines), in perfect agreement with the experimental observations^{17,18}. For $\mathcal{B}_{c1} < \mathcal{B} < \mathcal{B}_{c2}$, the chiral HO may also coexist with other still unidentified field-induced states. c. For $T < 3\text{K}$, the $d_{x^2-y^2}$ order parameter is nearly constant until $\mathcal{B} = \mathcal{B}_{c1}$, where it abruptly decreases. This is the gap seen in neutron scattering experiments⁸. Above the MCEP, the gap evolves smoothly with the field, explaining the dependence arising from bulk measurements¹². The saturation appearing in high fields does not give rise to any thermodynamic anomaly, rendering the chiral HO experimentally undetectable. d. The metamagnetic steps are accompanied by an abrupt increase of the magnetization. For higher temperatures the first order character becomes milder leading to a smooth evolution. e. The cascade of the metamagnetic transitions, appears due to additional band crossings at each $\mathcal{B}_c$ ³². The reconstruction of the Fermi surface increases steeply the carriers of the system and concomitantly the magnetization.

the density of carriers of the system and a concomitant steep enhancement of the magnetization³². For higher temperatures the first order character of the metamagnetic steps becomes milder, leading to a smoother increase of the magnetization in this region of fields.

The pronounced similarities presented in our phase diagram compared to Ref.^{17,18}, are accompanied by important ramifications arising from the finite chirality of the state. First and more importantly, the chiral HO

is present *everywhere* in this diagram, due to the enhanced critical temperature, originating from the orbital magnetic-field coupling. For magnetic fields $\mathcal{B}_{c1} < \mathcal{B} < \mathcal{B}_{c2}$, both order parameters of the chiral state suffer a severe decrease in their magnitude. Consequently, the chiral d-spin density wave state is still present in this region but unavoidably masked due to the destruction of its topological rigidity. The HO persists even for $\mathcal{B} \geq \mathcal{B}_{c2}$, behaving as a polarized paramagnetic metal.

Despite of the continuous presence of the chiral d-spin density wave order, the emergence of the MCEP leads to the generation of novel states at $\mathcal{B}_{c1}$, that in this case coexist with the chiral HO constituting phases *III*, *V* in Ref.¹⁸. It has been shown that, under quite generic conditions, the effect of a Zeeman field on a charge density wave can lead to a field-induced Spin Density Wave transition and vice versa^{32,33}. In this sense, the magnetic field may permit a number of possible induced states³⁴ such as the chiral spin singlet d-density wave state, studied in the context of the high-Tc superconductors^{25,27,29,30,35}, or even the spin singlet and triplet Pomeranchuk states^{36,37}.

Apart from the phase diagram, we have also studied in detail the thermoelectric response of this state. According to experimental observations, this compound is characterized by an anomalous thermoelectric behaviour up to 35T^{19,20}, where the HO has been considered to collapse²⁰. The arising Nernst signal has a positive sign and a giant magnitude of several $\mu\text{V}/\text{K}$, while the temperature evolution of the Nernst response resembles to a ‘tilted-hill’, demonstrating a peak at about 3-4K, where it reaches the value of $30\mu\text{V}/\text{K}$ for $\mathcal{B} \simeq 12\text{T}$. Up to now, the enhanced Nernst signal has been viewed as the signature of the semi-metallic character of this electron-hole compensated metal^{19,20}.

Here, by taking into account both topological and quasiparticle sources in computing the electric (σ_{xx}, σ_{xy}) and thermoelectric conductivity (α_{xx}, α_{xy}) tensor elements, we demonstrate that the Nernst response in the HO state can be understood in terms of the chiral d-spin density wave state. Using the values of the order parameters providing the phase diagram of Fig.1, we obtain a giant Nernst signal, that has a magnitude of about one order larger than the one observed in the experiments. The origin of the ‘tilted-hill’ Nernst signal is directly related to the chirality and the strong Fermi surface gapping. As presented in Ref.³⁰, the strong insulating character of the state forces the thermopower and the Nernst signal to become equal at a thermoelectric crossing point. In the vicinity of this point, the usually large values of the thermopower also imply a Nernst signal of the same magnitude, leading unavoidably to an enhancement of the latter. However, the thermoelectric rigidity and the tendency towards a giant Nernst signal are lost exactly at $\mathcal{B}_{c1}$. The steep decrease of the $d_{x^2-y^2}$ gap across this first order transition and the concomitant Fermi surface reconstruction which partially destroys the insulating properties of the state, lead to the full suppression of the response (Fig.2a) in accordance with Ref.²⁰.

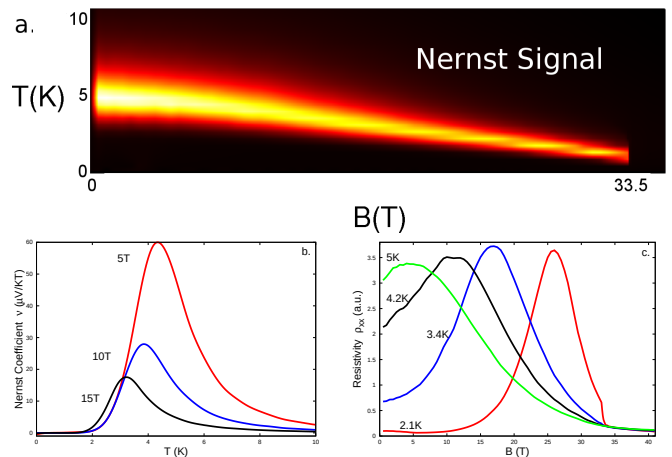


FIG. 2: a. $\mathcal{B} - T$ dependence of the self-consistently calculated Nernst signal. The arising Nernst response presents a large positive signal, of about one order larger than the experimentally observed¹⁹. The giant response originates from the topological robustness of the chiral state³⁰. The field destruction of the Nernst signal at $\mathcal{B}_{c1}$ agrees with the experiment²⁰, although here, it is accompanied by the dramatic reduction, rather than the collapse of the $d_{xy}, d_{x^2-y^2}$ order parameters. b. The Nernst coefficient $\nu = N/\mathcal{B}_z$ shows a ‘tilted-hill’ profile, with a pronounced peak in the region 3–5K following the experimental data¹⁹. c. Field dependence of the resistivity for several temperatures. For $T < T_o$, the presence of a ‘kink’, also found in experiments²⁰, may be naturally attributed to the field-enhancement of the d_{xy} component.

Furthermore, the Nernst coefficient exhibits a peaked structure with temperature and decreases upon raising the magnetic field already at 10K (Fig.2b). Notice that although this state is also present even above 17.5K, it does not lead to a large Nernst signal, becoming in this manner experimentally elusive. We have also calculated the resistivity for finite fields and temperatures. We observe in Fig.2c that the field dependence of the resistivity exhibits a kink with the increase of the magnetic field. This is a definite fingerprint of the field induced d_{xy} component and coincides with the experimental findings²⁰. This kink shifts to lower magnetic fields upon raising temperature, since the d_{xy} gap gradually weakens.

The HO exhibits an equally intricate behaviour under the application of pressure. Specifically, it switches to a large moment antiferromagnetic state (LMAF) of wave-vector $\mathbf{Q}_0 = (0, 0, 1)$, for pressure $p_c = 0.5\text{GPa}$ at $T=0\text{K}$ ^{10,11}. The intimate connection between the HO and LMAF^{4,10} and the emergent adiabatic continuity³⁸, has motivated the authors of Ref.^{39,40} to propose a $U(1) \equiv \text{SO}(2)$ theory for the unification of the HO and LMAF. We demonstrate that within our model, invoking an $\text{SO}(2)$ symmetry can fully explain the INS spectra.

In our case the $d_{x^2-y^2}$ order parameter is the dominant chiral HO component while the d_{xy} part is field-induced and depends on the former. As a matter of fact, the $\text{SO}(2)$ symmetry should emerge between the $id_{x^2-y^2}$ spin density wave (dSDW) state of wave-vector $\mathbf{Q}_1 = (1 \pm$

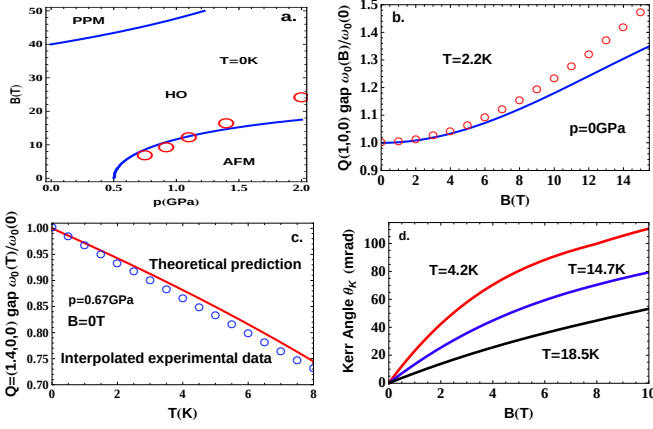


FIG. 3: a. The $p - B$ phase diagram obtained by the $SO(2)$ invariant Ginzburg-Landau model employed for unifying the hidden order (HO) and the large moment antiferromagnetism (LMAF). The first-order boundary separating these states is in accordance with the experimental data¹¹ (open circles). For larger fields, only the HO survives, collapsing into a polarized paramagnetic metal (PPM). b. Comparison of the theoretical magnetic-field dependence of the normalized energy gap of the Q spin excitation in the HO, to the neutron scattering data⁸. In the low-field limit, the theoretical curve fits to the experimental one. The Q spin excitation is identified as an orbital antiferromagnetic resonance. c. Comparison of the temperature dependence of the normalized energy gap of the Q_1 spin excitation in the LMAF, to the normalized temperature dependence of the LMAF order parameter. The very good agreement implies a possible spin-exciton formation due to an anisotropic s-wave momentum structure of the LMAF order parameter. e. Predicted Polar Kerr effect due to the intrinsic chirality of the proposed hidden order. The emergence of a chiral d-spin density wave below $T_o = 17.5K$, implies a field-induced large non-zero Kerr angle, even above T_o .

$0.4, 0, 0$) and the LMAF state $S_{Q_0}^z$, of wave-vector $Q_0 = (0, 0, 1) \equiv Q = (1, 0, 0)$. Rotating from the Q_1 -dSDW state to the s-wave Q -LMAF, demands the presence of an $id_{x^2-y^2}$ spin-0 orbital antiferromagnetic collective mode of momentum $Q_{orb} = (\pm 0.4, 0, 0)$. We have constructed a Ginzburg-Landau theory for the vector order parameter $n = (\Delta_2, S_{Q_0}^z)$, unifying HO and LMAF⁴¹. Although a phenomenological model, it succeeds in explaining the $p - B$ phase diagram (Fig.3a) of the competing HO and LMAF, and the field and temperature dependence of the INS energy gaps.

The HO exhibits an INS spectrum involving gapped spin excitations at Q_1 and Q . The first mode can be interpreted within the spin-exciton scenario. The observed value of $\omega_{Q_1}^0 = 4.5meV$, is practically field

independent⁸. According to the spin-exciton picture¹⁵, the value $\omega_{Q_1}^0/2 = 2.25meV$ should be indicative⁴² of the energy gap of the HO. This value agrees well with $\Delta_2 = 1.55meV$, which is the dominant gap for the HO in our framework. On the other hand, the Q spin resonance originates due to the spin-0 orbital antiferromagnetic collective mode. At first sight, the singlet character of this mode and the momentum it carries do not seem to agree with the observed resonance. Nevertheless, the presence of the dSDW, provides the complementary symmetry breaking so that this collective mode indeed affects the INS response. Fig.3b presents a comparison of our theoretical predictions compared to the experimental data⁸, focusing on the magnetic-field-dependence of the normalized energy gap $\omega_{Q_1}^0(2.2K, p = 0GPa, B_z)/\omega_{Q_1}^0(2.2K, p = 0GPa, 0T)$. We observe that in the low-field regime, our results exactly fit the experimental measurements.

In the LMAF state, a Bragg reflection appears at Q due to its pure AFM moment. Consequently, we expect suppression of the Q resonant channel, which is indeed experimentally verified¹¹. However, the Q_1 resonance still persists in the LMAF state with a larger gap¹⁰. The existence of an orbital antiferromagnetic mode cannot provide this resonance, even if LMAF is present. A possible explanation is that the LMAF order parameter has an unconventional s-wave momentum structure. In this case, the INS spectra would originate from the formation of a spin-exciton at Q_1 , and the spin excitation gap would be proportional to the LMAF order parameter. Here we compare the theoretically predicted normalized order parameter temperature dependence, $|n(T, p = 0.67GPa, 0T)|/|n(0K, p = 0.67GPa, 0T)|$, to the normalized energy gap temperature dependence found in experiments¹⁰. Indeed, we find a very good agreement (Fig.3c) that supports the possibility of an unconventional s-wave LMAF order parameter.

To detect the proposed chiral hidden order we predict a Polar Kerr effect originating from the inherent time-reversal violation²⁷. This type of measurement is an ideal probe of the intrinsic chirality of the state⁴³. More importantly, we expect that in our case the arising Kerr angle ϑ_K , will demonstrate a magnetic field dependence when the sample is cooled down in the presence of a static external magnetic field (Fig.3d). We find that the Kerr angle probed by a Sagnac interferometer ($\lambda = 1550nm$), is $\vartheta_K \simeq 128\Delta_1 mrad$ with Δ_1 in meV. The maximum value of $\Delta_1^{max} = 1.5meV$, sets an upper bound $\vartheta_K^{max} \simeq 190mrad$. The magnitude of the Kerr angle demonstrates that the expected response is very large and easily detectable. The observance of a finite Polar Kerr signal could constitute a sharp signature of our chiral hidden order state, unveiling the mechanisms that lead to the intricate URu_2Si_2 phenomenology.

* Electronic address: pkotetes@central.ntua.gr

¹ Palstra T. T. M. *et al.* Superconducting and Magnetic

- Transitions in the Heavy-Fermion System URu₂Si₂. *Phys. Rev. Lett.* **55**, 2727 (1985).
- ² Schlitz W. *et al.* Superconductivity and magnetic order in a strongly interacting fermi-system: URu₂Si₂. *Z. Phys. B* **62**, 171 (1986).
 - ³ Walker M. B. *et al.* Nature of the order parameter in the heavy-fermion system URu₂Si₂. *Phys. Rev. Lett.* **71**, 2630 (1993).
 - ⁴ Amitsuka H., and Yokoyama M. Inhomogeneous magnetism and hidden order in URu₂Si₂. *Physica B* **452**, 329 (2003).
 - ⁵ Takagi S. *et al.* No Evidence for Small-Moment Antiferromagnetism under Ambient Pressure in URu₂Si₂: Single-Crystal ²⁹Si NMR Study. *J. Phys. Soc. Jpn.* **76**, 033708 (2007).
 - ⁶ Mason T. E. *et al.* Non-trivial magnetic order in URu₂Si₂? *J. Phys.: Condens. Matter* **7**, 5089 (1995).
 - ⁷ Broholm C. *et al.* Magnetic excitations and ordering in the heavy-electron superconductor URu₂Si₂. *Phys. Rev. Lett.* **58**, 1467 (1987).
 - ⁸ Bourdarot F., Fak B., Habicht K., and Prokes K. Inflection point in the Magnetic Field Dependence of the Ordered Moment of URu₂Si₂ Observed by Neutron Scattering in Fields up to 17 T. *Phys. Rev. Lett.* **90**, 067203 (2003).
 - ⁹ Wiebe C. R. *et al.* Gapped itinerant spin excitations account for missing entropy in the hidden order state of URu₂Si₂. *Nature Physics* **3**, 1 (2007).
 - ¹⁰ Villaume A. *et al.* Signature of hidden order in heavy fermion superconductor URu₂Si₂: Resonance at the wave vector $Q_0=(1,0,0)$. *Phys. Rev. B* **78**, 012504 (2008).
 - ¹¹ Aoki D. *et al.* Field Reentrance of the Hidden Order State of URu₂Si₂ under Pressure. *J. Phys. Soc. Jpn.* **78**, 053701 (2009).
 - ¹² Mentink S. A. M. *et al.* Gap formation and magnetic ordering in URu₂Si₂ probed by high-field magnetoresistance. *Phys. Rev. B* **53**, (R) 6014 (1996).
 - ¹³ Elgazzar S. *et al.* Hidden order in URu₂Si₂ originates from Fermi surface gapping induced by dynamic symmetry breaking. *Nature Materials* **8**, 337 (2009).
 - ¹⁴ Santander-Syro F. *et al.* Fermi surface instability at the hidden-order transition of URu₂Si₂. *Nature Physics* **5**, 637 (2009).
 - ¹⁵ Balatsky A. V. *et al.* Incommensurate spin resonance in URu₂Si₂. *Phys. Rev. B* **79**, 214413 (2009).
 - ¹⁶ Ramirez A. P. *et al.* Nonlinear Susceptibility as a Probe of Tensor Spin order in URu₂Si₂. *Phys. Rev. Lett.* **68**, 2680 (1992).
 - ¹⁷ Harrison N., Jaime M., and Mydosh J. A. Reentrant Hidden Order at a Metamagnetic Quantum Critical End Point. *Phys. Rev. Lett.* **90**, 096402 (2003).
 - ¹⁸ Kim K. H. *et al.* Magnetic-Field-Induced Quantum Critical Point and Competing Order Parameters in URu₂Si₂. *Phys. Rev. Lett.* **91**, 256401 (2003).
 - ¹⁹ Bel R. *et al.* Thermoelectricity of URu₂Si₂: Giant Nernst effect in the hidden-order state. *Phys. Rev. B* **70**, 220501(R) (2004).
 - ²⁰ Levallois J. *et al.* On the destruction of the hidden order in URu₂Si₂ by a strong magnetic field. *Europhys. Lett.* **85**, 27003 (2009).
 - ²¹ Ikeda H., and Ohashi Y. Theory of Unconventional Spin Density Wave: A Possible Mechanism of the Micromagnetism in U-based Heavy Fermion Compounds. *Phys. Rev. Lett.* **81**, 3723 (1998).
 - ²² Chandra P., Coleman P., Mydosh J. A., and Tripathi V. Hidden Orbital Order in URu₂Si₂. *Nature* **417**, 831 (2002).
 - ²³ Virosztek A., Maki K., Dora B.. Micromagnetism in URu₂Si₂ and high temperature superconductors. *Int. J. Mod. Phys. B* **16**, 1667 (2002).
 - ²⁴ Zhu J.-X., and Balatsky A. V. Field induced $d_{x^2-y^2} + id_{xy}$ state in d-density-wave metals. *Phys. Rev. B* **65**, 132502 (2002).
 - ²⁵ Kotetes P., and Varelogiannis G. Magnetic-field-induced chiral particle-hole condensates. *Phys. Rev. B* **80**, 212401 (2009).
 - ²⁶ Kasahara Y. *et al.* Exotic Superconducting Properties in the Electron-Hole Compensated Heavy Fermion Semimetal URu₂Si₂. *Phys. Rev. Lett.* **99**, 116402 (2007).
 - ²⁷ Tewari S., Zhang C., Yakovenko V. M., and Das Sarma S. Time-Reversal Symmetry Breaking by a (d+id) Density-Wave State in Underdoped Cuprate Superconductors. *Phys. Rev. Lett.* **100**, 217004 (2008).
 - ²⁸ Kotetes P., and Varelogiannis G. Spontaneous Quantum Hall Effect in chiral d-density waves. *Europhys. Lett.* **84** (2008) 37012.
 - ²⁹ Zhang C., Tewari S., Yakovenko V. M., and Das Sarma S. Anomalous Nernst effect from a chiral d-density-wave state in underdoped cuprate superconductors. *Phys. Rev. B* **78**, 174508 (2008).
 - ³⁰ Kotetes P., and Varelogiannis G. Chirality Induced Tilted-Hill Giant Nernst Signal. arXiv:0911.2512.
 - ³¹ Grigera S. A. *et al.* Magnetic Field-Tuned Quantum Criticality in the Metallic Ruthenate Sr₃Ru₂O₇. *Science* **294**, 329 (2001).
 - ³² Aperis A., Varelogiannis G. and Littlewood P. B. Metamagnetic Transitions and CMR from the Coexistence and Competition of CDW, SDW and FM. *J. Phys.: Conf. Ser.* **150**, 042007 (2009).
 - ³³ Aperis A. *et al.* New Field-Induced Spin Density Wave Phenomena from the Pauli Terms in Excitonic Insulators. *Europhys. Lett.* **83**, 67008 (2008).
 - ³⁴ Tsonis S., Kotetes P., Varelogiannis G., and Littlewood P.B. Patterns of coexisting superconducting and particle-hole condensates. *J. Phys.: Condens. Matter* **20**, 434234 (2008).
 - ³⁵ Kotetes P., and G. Varelogiannis. Meissner effect without superconductivity from a chiral d-density wave. *Phys. Rev. B* **78**, 220509(R) (2008).
 - ³⁶ Yamase H., and Kohno H. *J. Phys. Soc. Jpn.* **69**, 332 (2000).
 - ³⁷ Wu C., Sun K., Fradkin E., and Zhang S.-C. Fermi liquid instabilities in the spin channel. *Phys. Rev. B* **75**, 115103 (2007).
 - ³⁸ Jo Y. J. *et al.* Field-Induced Fermi Surface Reconstruction and Adiabatic Continuity between Antiferromagnetism and the Hidden-Order State in URu₂Si₂. *Phys. Rev. Lett.* **98**, 166404 (2007).
 - ³⁹ Haule K., and Kotliar G. Arrested Kondo effect and hidden order in URu₂Si₂. *Nature Physics* **5**, 796 (2009).
 - ⁴⁰ Haule K., and Kotliar G. Complex Landau Ginzburg Theory of the Hidden Order in URu₂Si₂. arXiv:0907.3892.
 - ⁴¹ Demler E., Hanke W., and Zhang S.-C. SO(5) theory of antiferromagnetism and superconductivity. *Rev. Mod. Phys.* **76**, 909 (2004).
 - ⁴² Ismer J.-P., Eremin I., and Morr D.K. Dynamical spin susceptibility and the resonance peak in the pseudogap region of the underdoped cuprate superconductors. *Phys. Rev. B* **73**, 104519 (2006).
 - ⁴³ Kapitulnik A. *et al.* Polar Kerr Effect as Probe for Time-

I. SUPPLEMENTARY MATERIAL

II. MEAN-FIELD DECOUPLING AND ORDER PARAMETER SYMMETRIES

Based on the phenomenology of URu₂Si₂, we have proposed that the chiral d-spin density wave state orders at an incommensurate wave vector $\mathbf{Q}_1 = (1 \pm 0.4, 0, 0)$. Describing microscopically a chiral state with this ordering wave-vector, demands taking into account the main four Fermi lines that give rise to this nesting symmetry¹. This is a very complex and unnecessary task, since our results do not depend on the microscopic details of the model. Our results concerning the anomalous Hall thermoelectric transport and the energy gap of the collective mode, are based solely on the topological content and the symmetry properties of this state. Moreover, the phase diagram and the metamagnetic transitions are also based on the general principles of itinerant metamagnetism, according to which this phenomenon originates from band crossing². Under these conditions it is permissible to consider the existence of a nesting condition for the paramagnetic system $\varepsilon(\mathbf{k} + \mathbf{Q}_1) \simeq -\varepsilon(\mathbf{k}) = -[-2t(\cos k_x + \cos k_y)]$ that is exact only for the commensurate ordering wave-vector (π, π) . This condition, should stand for the real bands of URu₂Si₂, and within our approximate simple model we perform a simulation of this situation. Finally, we have considered $\Delta_1(\mathbf{k}) = \Delta_1 \sin k_x \sin k_y$, $\Delta_2(\mathbf{k}) = \Delta_2(\cos k_x - \cos k_y)$ with $\Delta_{1,2} = \Delta_{1,2}^*$.

To study the phase diagram of the chiral d-spin density wave state we consider that it is driven by an inter-site Coulomb repulsion including nearest and next-nearest neighbours

$$\mathcal{V}_{int} = \sum_{i \neq j} V_{i,j} n_i n_j = - \sum_{i \neq j} \sum_{s,s'} V_{i,j} c_{i,s}^\dagger c_{j,s'} c_{j,s'}^\dagger c_{i,s} = -\frac{1}{v} \sum_{\mathbf{k}, \mathbf{k}'} \sum_{s,s'} V(\mathbf{k} - \mathbf{k}') c_{\mathbf{k},s}^\dagger c_{\mathbf{k}+\mathbf{Q},s'} c_{\mathbf{k}'+\mathbf{Q},s'}^\dagger c_{\mathbf{k}',s}, \quad (1)$$

with $s, s' = \uparrow, \downarrow$ and $V(\mathbf{q}) = 2V'(\cos q_x + \cos q_y) + 4V'' \cos q_x \cos q_y$. The momenta $\mathbf{k}, \mathbf{k}'$ belong to the whole Brillouin zone ($\mathcal{B.Z.}$) if $\mathbf{Q}$ is incommensurate and in the reduced Brillouin zone if $\mathbf{Q}$ is commensurate satisfying $\mathbf{k} + 2\mathbf{Q} = \mathbf{k}$. The potential is separable providing $V(\mathbf{k} - \mathbf{k}') = \sum_n V_n f_n(\mathbf{k}) f_n(\mathbf{k}')$ with $n = 1, 2, \dots, 8$ corresponding to the form factors $f_n(\mathbf{k})$: $\cos k_x \pm \cos k_y$, $\sin k_x \pm \sin k_y$, $\cos k_x \cos k_y$, $\sin k_x \sin k_y$, $\cos k_x \sin k_y$, $\sin k_x \cos k_y$ with the driving potentials $V_n = V'$ for $n = 1, 2, 3, 4$ and $V_n = 4V''$ for the rest. Then within a mean-field treatment we introduce the staggered order parameters $\Delta_Q^{\uparrow\uparrow}(\mathbf{k}), \Delta_Q^{\downarrow\downarrow}(\mathbf{k}), \tilde{\Delta}_Q^{\uparrow\uparrow}(\mathbf{k}), \tilde{\Delta}_Q^{\downarrow\downarrow}(\mathbf{k})$ as

$$\Delta_Q^{ss}(\mathbf{k}) = -\frac{1}{v} \sum_{\mathbf{k}'} V(\mathbf{k} - \mathbf{k}') \langle c_{\mathbf{k}'+\mathbf{Q},s}^\dagger c_{\mathbf{k}',s} \rangle = \sum_n \Delta_{Q,n}^{ss}(\mathbf{k}) \quad s = \uparrow, \downarrow, \quad (2)$$

$$\tilde{\Delta}_Q^{ss}(\mathbf{k}) = -\frac{1}{v} \sum_{\mathbf{k}'} V(\mathbf{k} - \mathbf{k}') \langle c_{\mathbf{k}',s}^\dagger c_{\mathbf{k}'+\mathbf{Q},s} \rangle = \sum_n [\Delta_{Q,n}^{ss}(\mathbf{k})]^* \quad s = \uparrow, \downarrow, \quad (3)$$

and the corresponding irreducible $\mathbf{k}$ -independent staggered order parameters

$$\Delta_{Q,n}^{ss} = -\frac{1}{v} \sum_{\mathbf{k}} V_n f_n(\mathbf{k}) \langle c_{\mathbf{k}+\mathbf{Q},s}^\dagger c_{\mathbf{k},s} \rangle \quad s = \uparrow, \downarrow. \quad (4)$$

The interaction decouples in the following way

$$\begin{aligned} \mathcal{V}_{int} &= \sum_{\mathbf{k}} \left\{ \Delta_Q^{\uparrow\uparrow}(\mathbf{k}) c_{\mathbf{k},\uparrow}^\dagger c_{\mathbf{k}+\mathbf{Q},\uparrow} + \Delta_Q^{\downarrow\downarrow}(\mathbf{k}) c_{\mathbf{k},\downarrow}^\dagger c_{\mathbf{k}+\mathbf{Q},\downarrow} + h.c. \right\} + \frac{1}{v} \sum_{\mathbf{k}, \mathbf{k}'} \sum_{s,s'} V(\mathbf{k} - \mathbf{k}') \langle c_{\mathbf{k},s}^\dagger c_{\mathbf{k}+\mathbf{Q},s'} \rangle \langle c_{\mathbf{k}'+\mathbf{Q},s'}^\dagger c_{\mathbf{k}',s} \rangle \\ &= \sum_{\mathbf{k}} \left\{ \Delta_Q^{\uparrow\uparrow}(\mathbf{k}) c_{\mathbf{k},\uparrow}^\dagger c_{\mathbf{k}+\mathbf{Q},\uparrow} + \Delta_Q^{\downarrow\downarrow}(\mathbf{k}) c_{\mathbf{k},\downarrow}^\dagger c_{\mathbf{k}+\mathbf{Q},\downarrow} + h.c. \right\} + v \sum_n \sum_s \frac{|\Delta_{Q,n}^{ss}|^2}{V_n} \end{aligned} \quad (5)$$

with v the volume of the corresponding $\mathcal{B.Z.}$. By introducing the spinor $\Psi_{\mathbf{k}}^\dagger = (c_{\mathbf{k},\uparrow}^\dagger, c_{\mathbf{k},\downarrow}^\dagger, c_{\mathbf{k}+\mathbf{Q},\uparrow}^\dagger, c_{\mathbf{k}+\mathbf{Q},\downarrow}^\dagger)$ and by using the isospin and spin Pauli matrices τ_i, σ_i with $i = 1, 2, 3$ complemented by the related unit matrices τ_0, σ_0 , we furnish a representation of the 4×4 mean-field hamiltonian as Kronecker products of the form

$\tau_\mu \otimes \sigma_\nu$ where $\mu, \nu = 0, 1, 2, 3$ (for simplicity we omit $\otimes$). The most general chiral d-spin density wave state is defined as $\Delta_{\mathbf{Q}}^z(\mathbf{k}) = \Delta_1(\mathbf{k}) - i\Delta_2(\mathbf{k})$. Moreover we introduce the kinetic term of the paramagnetic state $\mathcal{H}_0 = \sum_{\mathbf{k}, s} \left\{ (\varepsilon(\mathbf{k}) - \mu) c_{\mathbf{k}, s}^\dagger c_{\mathbf{k}, s} + (\varepsilon(\mathbf{k} + \mathbf{Q}) - \mu) c_{\mathbf{k} + \mathbf{Q}, s}^\dagger c_{\mathbf{k} + \mathbf{Q}, s} \right\}$ along with a chemical potential μ . Putting together all these terms and using the fact that in the spin-triplet state $\Delta_{\mathbf{Q}}^z = \Delta_{\mathbf{Q}}^{\uparrow\uparrow} = -\Delta_{\mathbf{Q}}^{\downarrow\downarrow}$, we obtain the quasiparticle Hamiltonian

$$\begin{aligned} \mathcal{H}_{q-p} &= \sum_{\mathbf{k}} \begin{pmatrix} c_{\mathbf{k}, \uparrow}^\dagger & c_{\mathbf{k}, \downarrow}^\dagger & c_{\mathbf{k} + \mathbf{Q}, \uparrow}^\dagger & c_{\mathbf{k} + \mathbf{Q}, \downarrow}^\dagger \end{pmatrix} \\ &\quad \begin{pmatrix} \varepsilon(\mathbf{k}) - \mu & 0 & \Delta_1(\mathbf{k}) - i\Delta_2(\mathbf{k}) & 0 \\ 0 & \varepsilon(\mathbf{k}) - \mu & 0 & -\Delta_1(\mathbf{k}) + i\Delta_2(\mathbf{k}) \\ \Delta_1^*(\mathbf{k}) + i\Delta_2^*(\mathbf{k}) & 0 & \varepsilon(\mathbf{k} + \mathbf{Q}) - \mu & 0 \\ 0 & -\Delta_1^*(\mathbf{k}) - i\Delta_2^*(\mathbf{k}) & 0 & \varepsilon(\mathbf{k} + \mathbf{Q}) - \mu \end{pmatrix} \begin{pmatrix} c_{\mathbf{k}, \uparrow}^\dagger \\ c_{\mathbf{k}, \downarrow}^\dagger \\ c_{\mathbf{k} + \mathbf{Q}, \uparrow}^\dagger \\ c_{\mathbf{k} + \mathbf{Q}, \downarrow}^\dagger \end{pmatrix} \\ &= \sum_{\mathbf{k}} \Psi_{\mathbf{k}}^\dagger \left\{ \frac{\Delta_1(\mathbf{k}) + \Delta_1^*(\mathbf{k})}{2} \tau_1 \sigma_3 + \frac{\Delta_1(\mathbf{k}) - \Delta_1^*(\mathbf{k})}{2} i\tau_2 \sigma_3 - i \frac{\Delta_2(\mathbf{k}) - \Delta_2^*(\mathbf{k})}{2} \tau_1 \sigma_3 + \frac{\Delta_2(\mathbf{k}) + \Delta_2^*(\mathbf{k})}{2} \tau_2 \sigma_3 \right. \\ &\quad \left. + \frac{\varepsilon(\mathbf{k}) + \varepsilon(\mathbf{k} + \mathbf{Q})}{2} \tau_0 \sigma_0 + \frac{\varepsilon(\mathbf{k}) - \varepsilon(\mathbf{k} + \mathbf{Q})}{2} \tau_3 \sigma_0 - \mu \tau_0 \sigma_0 \right\} \Psi_{\mathbf{k}}, \end{aligned} \quad (6)$$

and the elastic energy needed to build up the two density wave gaps

$$\mathcal{H}_{\Delta^2} = 2v \left(\frac{|\Delta_1|^2}{4V''} + \frac{|\Delta_2|^2}{V'} \right). \quad (7)$$

We now exploit the constraints that are imposed to the order parameters when the ordering vector $\mathbf{Q}$ is commensurate, satisfying $\mathbf{k} + 2\mathbf{Q} = \mathbf{k}$. The translation operation $t_{\mathbf{Q}}$ corresponds to the shifting $\mathbf{k} \rightarrow \mathbf{k} + \mathbf{Q}$. Since $\mathbf{k} + 2\mathbf{Q} = \mathbf{k}$ we have $t_{\mathbf{Q}}^2 = 1 \Rightarrow \pm 1$. This means that this discrete symmetry transformation can divide a function into two irreducible representations, the periodic and the anti-periodic under $t_{\mathbf{Q}}$. This operation induces a transformation $\hat{t}_{\mathbf{Q}}$ in the spinor space, defined as

$$\hat{t}_{\mathbf{Q}} \Psi_{\mathbf{k}} \hat{t}_{\mathbf{Q}}^\dagger = \tau_1 \sigma_0 \Psi_{\mathbf{k}}. \quad (8)$$

An element in the spinor representation of the form $\sum_{\mathbf{k}} \Psi_{\mathbf{k}}^\dagger \Pi(\mathbf{k}) \Psi_{\mathbf{k}}$ is invariant under translation, which is a symmetry transformation of the system, only if $\Pi(\mathbf{k})$ transforms in the following way

$$\hat{t}_{\mathbf{Q}} \Pi(\mathbf{k}) \hat{t}_{\mathbf{Q}}^\dagger = \tau_1 \sigma_0 \Pi(\mathbf{k}) \tau_1 \sigma_0. \quad (9)$$

In this manner we may label the elements of the spinor space with representations of the traslation operation. It is straightforward to show that the elements $\tau_{0,1}\sigma_\nu$ remain invariant under translation while the rest i.e. $\tau_{2,3}\sigma_\nu$ are anti-periodic changing their sign ($\nu = 0, 1, 2, 3$). This implies that for a chiral spin-triplet (and singlet) d-density wave we must have $\Delta_1(\mathbf{k} + \mathbf{Q}) = \Delta_1(\mathbf{k}) \Rightarrow \Delta_1 = \Delta_1^*$ and $\Delta_2(\mathbf{k} + \mathbf{Q}) = -\Delta_2(\mathbf{k}) \Rightarrow \Delta_2 = -\Delta_2^*$. Nevertheless, there is no such constraint when the ordering wave-vector is incommensurate like in our case.

III. INTRINSIC ORBITAL MOMENT AND MAGNETIC FIELD COUPLING

With these definitions we may write the quasiparticle hamiltonian in the condensed form $\mathcal{H}_{q-p} = \sum_{\mathbf{k}} \Psi_{\mathbf{k}}^\dagger \{ \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\tau} - \mu \} \Psi_{\mathbf{k}}$ where we have introduced the vector $\hat{\mathbf{g}}(\mathbf{k}) = (\Delta_1(\mathbf{k})\sigma_3, \Delta_2(\mathbf{k})\sigma_3, \varepsilon(\mathbf{k})\sigma_0)$. Diagonalizing the above hamiltonian yields the eigenstates $|\Phi_{s,\nu}(\mathbf{k})\rangle$ with energy dispersions $E_{s,\nu}(\mathbf{k}) = -\mu + \nu E(\mathbf{k})$ and $\nu = \pm, s = \uparrow, \downarrow$, $E(\mathbf{k}) = |\hat{\mathbf{g}}(\mathbf{k})| = \sqrt{\varepsilon^2(\mathbf{k}) + |\Delta_{\mathbf{Q}}^z(\mathbf{k})|^2}$. The non trivial topological content of this Hamiltonian generates a non zero $U(1)$ Berry connection³ $\mathcal{A}_{s,\nu}(\mathbf{k}) = \langle \Phi_{s,\nu}(\mathbf{k}) | i\nabla_{\mathbf{k}} | \Phi_{s,\nu}(\mathbf{k}) \rangle$ and a corresponding Berry curvature defined as

$\Omega_{s,\nu}(\mathbf{k}) = \nabla_{\mathbf{k}} \times \mathcal{A}_{s,\nu}(\mathbf{k}) = \Omega_{s,\nu}^z(\mathbf{k}) \hat{\mathbf{z}}$, i.e. oriented along the z -axis. The detailed expression for the Berry curvature reads⁴⁻⁷

$$\Omega_{s,\nu}^z(\mathbf{k}) = \frac{1}{2} \text{Tr}_\sigma \left\{ \frac{-\nu a^2}{2E^3(\mathbf{k})} \hat{\mathbf{g}}(\mathbf{k}) \cdot \left(\frac{\partial \hat{\mathbf{g}}(\mathbf{k})}{\partial k_x} \times \frac{\partial \hat{\mathbf{g}}(\mathbf{k})}{\partial k_y} \right) \right\}. \quad (10)$$

with $s, \nu = \pm$. We observe that the Berry curvature is not depending on spin while it just changes sign when $\nu = \pm$. The intrinsic orbital moment of this state is straightforward calculated using the definition³

$$\mathbf{m}_{s,\nu}(\mathbf{k}) = \frac{e}{2\hbar i} \langle \nabla_{\mathbf{k}} \Phi_{s,\nu}(\mathbf{k}) | \times [\mathcal{H}(\mathbf{k}) - E_{s,\nu}(\mathbf{k})] | \nabla_{\mathbf{k}} \Phi_{s,\nu}(\mathbf{k}) \rangle = \frac{e\nu}{\hbar} E(\mathbf{k}) \Omega_{s,\nu}(\mathbf{k}). \quad (11)$$

One may observe that the orbital moment is band independent. When we apply a magnetic field, the system interacts with both the Zeeman and the orbital moment $m_z(\mathbf{k}) = eE(\mathbf{k})\Omega_{s,+}^z(\mathbf{k})/\hbar$ yielding the following interacting Hamiltonian $\mathcal{H}_B(\mathbf{k}) = -(\mu_B \tau_0 \sigma_3 - m_z(\mathbf{k}) \tau_0 \sigma_0) \mathcal{B}$. The inclusion of the magnetic coupling leads to the four field dependent eigenenergies $E_{s,\nu}^B(\mathbf{k}) = -\mu_B s - m_z(\mathbf{k}) - \mu + \nu E(\mathbf{k})$ with $\nu, s = \pm$ corresponding to the conduction and valence bands of the upper and lower spin sectors respectively.

IV. FREE ENERGY AND SELF-CONSISTENCY EQUATIONS

Having set up the microscopic description of the chiral d-spin density wave condensate, interacting with both Zeeman and the intrinsic orbital moments with a perpendicular magnetic field, we may solve the self-consistency equations that derive from the minimization of the free-energy functional

$$\mathcal{F} = 2v \left(\frac{\Delta_1^2}{4V''} + \frac{\Delta_2^2}{V'} \right) - \frac{1}{\beta} \sum_{\mathbf{k}, s, \nu} \ln \left(1 + e^{-\beta E_{s,\nu}^B(\mathbf{k})} \right), \quad (12)$$

with $t = 50\text{meV}$, $\mu = 0.69\text{meV}$, $\mu_B = 0.058\text{meV/T}$, $a = 5\text{\AA}$, $V' = 23.5\text{meV}$ and $V'' = 35.25\text{meV}$. Minimization of the free energy yields the following two self-consistency equations, that determine the order parameters of the chiral d-spin density wave⁵

$$\frac{\partial \mathcal{F}}{\partial \Delta_i} = 0 \Rightarrow \Delta_i = \frac{V_i}{2v} \sum_{\mathbf{k}, s, \nu} \left\{ -\nu \Delta_i \frac{f_i^2(\mathbf{k})}{2E(\mathbf{k})} - \frac{ea^2 t}{\hbar} \mathcal{B}_z \tilde{\Delta}_i \frac{S(\mathbf{k})}{E^2(\mathbf{k})} \left[1 - 2 \left(\frac{\Delta_i(\mathbf{k})}{E(\mathbf{k})} \right)^2 \right] \right\} n_F [E_{s,\nu}^B(\mathbf{k})], \quad (13)$$

with $V_1 = 4V''$, $V_2 = V'$, $\tilde{\Delta}_{1,2} = \Delta_{2,1}$, $S(\mathbf{k}) = \sin^2 k_x \cos^2 k_y + \sin^2 k_y$ and n_F the Fermi-Dirac distribution.

V. MAGNETIZATION AND THERMOELECTRIC RESPONSE

As far as the magnetic and transport properties are concerned, we have used the expressions found in the theory of orbital magnetization³. Specifically, the magnetization is the summation of both spin and orbital contributions in the following way $\mathcal{M}_z^B = \mathcal{M}_{z,\text{spin}}^B + \mathcal{M}_{z,\text{orb}}^B$

$$\mathcal{M}_{z,\text{spin}}^B = \frac{1}{v} \sum_{\mathbf{k}, s, \nu} \left\{ \left(1 + \frac{e\mathcal{B}a^2}{\hbar} \Omega_{s,\nu}^z(\mathbf{k}) \right) \mu_B s n_F [E_{s,\nu}^B(\mathbf{k})] \right\}, \quad (14)$$

$$\mathcal{M}_{z,\text{orb}}^B = \frac{1}{v} \sum_{\mathbf{k}, s, \nu} \left\{ \left(1 + \frac{e\mathcal{B}a^2}{\hbar} \Omega_{s,\nu}^z(\mathbf{k}) \right) m_z(\mathbf{k}) n_F [E_{s,\nu}^B(\mathbf{k})] + \frac{ea^2}{\hbar} \Omega_{s,\nu}^z(\mathbf{k}) k_B T \ln \left(1 + e^{-E_{s,\nu}^B(\mathbf{k})/k_B T} \right) \right\}. \quad (15)$$

The above expressions include the Berry phase correction to the electronic density of states, as this is apparent from the factor $\left(1 + \frac{e\mathcal{B}a^2}{\hbar} \Omega_{s,\nu}^z(\mathbf{k}) \right)$ in the first equation.

As far as the transport properties are concerned, we have taken into account both topological ($\sigma_{xy,top}^{\mathcal{B}}, \alpha_{xy,top}^{\mathcal{B}}$) and quasiparticle contributions ($\sigma_{xy,q-p}^{\mathcal{B}}, \alpha_{xy,q-p}^{\mathcal{B}}$) in calculating the Hall transport, while we have incorporated the Berry phase corrections in the scattering time and density states of the system. We have used $\tau_{s,\nu}(\mathbf{k}) \equiv \tau = 3.3 \cdot 10^{-13}s$. Based on experimental data⁸ $m^* = 25m_e$, and $\omega_c\tau(\mathcal{B} = 1T) = 0.08$, the estimated scattering time is of the order of $10^{-12}s$. In order to illustrate the chirality induced giant Nernst signal, we have on purpose selected a 3 times smaller relaxation time so to demonstrate that the possible enhancement of the quasiparticle contribution due to a large τ , is not crucial for the anomalous Hall thermoelectricity. In finite magnetic fields, the initially constant relaxation time, becomes field and momentum dependent in the following manner

$$\tau_{s,\nu}^{\mathcal{B}}(\mathbf{k}) = \frac{\tau_{s,\nu}(\mathbf{k})}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})} = \frac{\tau}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})}. \quad (16)$$

The electric and thermoelectric coefficients read

$$\sigma_{xx}^{\mathcal{B}} = -\frac{1}{v} \sum_{\mathbf{k},s,\nu} \frac{n'_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})]}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})} \left(\frac{\tau_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{\hbar} \right) [v_{s,\nu}^{x,\mathcal{B}}(\mathbf{k})]^2, \quad (17)$$

$$\alpha_{xx}^{\mathcal{B}} = +\frac{1}{v} \sum_{\mathbf{k},s,\nu} \frac{n'_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})]}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})} \left(\frac{\tau_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{\hbar} \right) [v_{s,\nu}^{x,\mathcal{B}}(\mathbf{k})]^2 \left(\frac{E_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{k_B T} \right), \quad (18)$$

$$\sigma_{xy,top}^{\mathcal{B}} = -\frac{1}{v} \sum_{\mathbf{k},s,\nu} n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] \Omega_{s,\nu}^z(\mathbf{k}), \quad (19)$$

$$\alpha_{xy,top}^{\mathcal{B}} = +\frac{1}{v} \sum_{\mathbf{k},s,\nu} \left\{ \left(\frac{E_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{k_B T} \right) n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] + \ln \left(1 + e^{-E_{s,\nu}^{\mathcal{B}}(\mathbf{k})/k_B T} \right) \right\} \Omega_{s,\nu}^z(\mathbf{k}), \quad (20)$$

$$\sigma_{xy,q-p}^{\mathcal{B}} = -\frac{1}{v} \sum_{\mathbf{k},s,\nu} \frac{n'_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})]}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})} \left(\frac{\tau_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{\hbar} \right)^2 \frac{ea^2\mathcal{B}}{\hbar} v_{s,\nu}^x(\mathbf{k}) \left(\varepsilon_{ijz} v_{s,\nu}^{j,\mathcal{B}}(\mathbf{k}) \frac{\partial}{\partial k_i} \right) v_{s,\nu}^{y,\mathcal{B}}(\mathbf{k}), i, j = x, y, \quad (21)$$

$$\alpha_{xy,q-p}^{\mathcal{B}} = -\frac{1}{v} \sum_{\mathbf{k},s,\nu} \frac{n'_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})]}{1 + \frac{e}{\hbar}\mathcal{B}\Omega_{s,\nu}^z(\mathbf{k})} \left(\frac{\tau_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{\hbar} \right)^2 \frac{ea^2\mathcal{B}}{\hbar} v_{s,\nu}^x(\mathbf{k}) \left(\varepsilon_{ijz} v_{s,\nu}^{j,\mathcal{B}}(\mathbf{k}) \frac{\partial}{\partial k_i} \right) v_{s,\nu}^{y,\mathcal{B}}(\mathbf{k}) \left(\frac{E_{s,\nu}^{\mathcal{B}}(\mathbf{k})}{k_B T} \right), i, j = x, y. \quad (22)$$

with units $[\sigma] = ea^2/\hbar$ and $[\alpha] = (k_B/e)[\sigma]$. We have also introduced the field dependent velocities $\mathbf{v}_{s,\nu}^{\mathcal{B}}(\mathbf{k}) = \nabla_{\mathbf{k}} E_{s,\nu}^{\mathcal{B}}(\mathbf{k})$. The Nernst signal and the resistivity are calculated from the following expressions

$$\mathcal{N} = \frac{E_y}{-\partial_x T} = \frac{\sigma_{xx}^{\mathcal{B}} \alpha_{xy}^{\mathcal{B}} - \alpha_{xx}^{\mathcal{B}} \sigma_{xy}^{\mathcal{B}}}{\sigma_{xx}^{\mathcal{B}} \sigma_{yy}^{\mathcal{B}} + \sigma_{xy}^{\mathcal{B}} \sigma_{xy}^{\mathcal{B}}}, \quad \rho_{xx}^{\mathcal{B}} = \frac{\sigma_{xx}^{\mathcal{B}}}{\sigma_{xx}^{\mathcal{B}} \sigma_{yy}^{\mathcal{B}} + \sigma_{xy}^{\mathcal{B}} \sigma_{xy}^{\mathcal{B}}}. \quad (23)$$

VI. GINZBURG-LANDAU THEORY OF THE MAGNETIC-FIELD-INDUCED CHIRAL D-SPIN DENSITY WAVE STATE

We may construct a simple phenomenological model for the field-induced chiral hidden order proposed in this manuscript. The numerical solution of the equations, points to the following Ginzburg-Landau picture for the chiral d-spin density wave order

$$\mathcal{F} = \alpha_1 \frac{\Delta_1^2}{2} + \alpha(T - T_o) \frac{\Delta_2^2}{2} + \beta \frac{\Delta_2^4}{4} - g \Delta_1 \Delta_2 \mathcal{B}_z. \quad (24)$$

The phenomenological constants $\alpha_{1,2}, \beta$ and the field $\mathcal{B}_z$, are positive. The coefficient α_1 ensures that the d_{xy} component is magnetic-field induced⁹. The important result discerned from the numerical analysis, concerns the sign of the orbital coupling g , that *is also positive*. With this convention, $\Delta_{1,2}$ have the same sign. The mean-field solution for the Δ_1 component yields

$$\frac{\partial \mathcal{F}}{\partial \Delta_1} = 0 \Rightarrow \alpha_1 \Delta_2 = g \Delta_2 \mathcal{B}_z. \quad (25)$$

One may ‘integrate out’ the induced Δ_1 component and obtain an effective theory only in terms of the driving $d_{x^2-y^2}$ order parameter Δ_2 . This is straightforward, yielding

$$\mathcal{F}_{eff} = \alpha(T - T_o) \frac{\Delta_2^2}{2} + \beta \frac{\Delta_2^4}{4} - \frac{g^2}{\alpha_1} \Delta_2^2 \mathcal{B}_z^2 = \alpha [T - T_o(\mathcal{B}_z)] \frac{\Delta_2^2}{2} + \beta \frac{\Delta_2^4}{4}. \quad (26)$$

Notice, that since $\alpha_1 > 0$, the quadratic magnetic-field-coupling leads to an enhanced critical temperature⁹ $T_o(\mathcal{B}_z) = T_o + \frac{g^2}{\alpha_1} \mathcal{B}_z^2$ for the $d_{x^2-y^2}$ component and consequently for the chiral order. In the magnetic-field-induced chiral d-spin density wave, the Δ_2 order parameter is driving the transition.

VII. SO(2) MODEL FOR UNIFYING THE CHIRAL HIDDEN ORDER AND THE LARGE MOMENT ANTIFERROMAGNETIC STATE

As we have previously shown, in the case of a magnetic-field-induced chiral d-spin density wave state, we may construct an effective theory solely in terms of the dominant $d_{x^2-y^2}$ order parameter. Essentially, this is the order parameter of the chiral hidden order that we expect to demonstrate a degeneracy with the large moment antiferromagnetic state. To handle the emergent SO(2) symmetry between the d-spin density wave component Δ_2 of the chiral hidden order and the large moment antiferromagnetic state S_Q^z , we shall employ a simple SO(2) invariant Ginzburg-Landau model. The order parameters can be combined in a vector order parameter $\mathbf{n} = (\Delta_2, S_Q^z)$ as in reference¹⁰. For a microscopic formulation based on operators, a more realistic model should be used. The phenomenology of URu₂Si₂ imposes the emergence of a first order transition from the hidden order to the antiferromagnetic state upon raising the pressure $p^{11,12}$. At ambient pressure URu₂Si₂ 5f-electrons condense into the HO state, implying that the latter should be promoted compared to antiferromagnetism. This calls for pressure dependent coefficients for the two order parameters that become equal at the critical pressure p_c in which HO switches to LMAF. Since we study static order parameters our free energy functional is written

$$\mathcal{F} = \alpha [T - T_{c,1}(p, \mathcal{B}_z)] \frac{\Delta_2^2}{2} + \alpha [T - T_{c,2}(p, \mathcal{B}_z)] \frac{(S_Q^z)^2}{2} + \beta \frac{\Delta_2^4}{4} + \beta \frac{(S_Q^z)^4}{4} + \beta \frac{\Delta_2^2 (S_Q^z)^2}{2}, \quad (27)$$

with

$$T_{c,1}(p, \mathcal{B}_z) = T_o(p) - g_o(p) \mathcal{B}_z^2, \quad (28)$$

$$T_{c,2}(p, \mathcal{B}_z) = T_a(p) - g_a(p) \mathcal{B}_z^2. \quad (29)$$

We have introduced the positive coefficients α, β and the pressure dependent critical temperatures $T_o(p), T_a(p)$ and magnetic-field couplings $g_o(p), g_a(p)$, corresponding to the HO and the large moment antiferromagnetism, respectively. The critical temperatures and the coupling strengths will be considered to have the following pressure dependence

$$T_o(p) = T_o(0) + [T_c - T_o(0)] \frac{p}{p_c}, \quad (30)$$

$$T_a(p) = \frac{p_1 T_c - p_c T_a(p_1)}{p_1 - p_c} + \frac{T_a(p_1) - T_c}{p_1 - p_c} p, \quad (31)$$

$$g_o(p) = v_o + u_o p, \quad (32)$$

$$g_a(p) = v_a + u_a p, \quad (33)$$

with T_c the critical temperature at the critical pressure p_c where the SO(2) symmetry is exact, $T_o(0)$ the critical temperature of the hidden order at zero pressure and $T_a(p_1)$ the critical temperature of the antiferromagnetic phase for a pressure $p_1 > p_c$. By setting $\mathbf{n} = (\Delta_2, S_Q^z)$, the free energy functional becomes

$$\mathcal{F} = \sum_{i=1,2} \left\{ \alpha \left[T - T_{c,i}(p, \mathcal{B}_z) \right] \frac{n_i^2}{2} \right\} + \beta \frac{|\mathbf{n}|^4}{4}. \quad (34)$$

Minimizing the free energy functional, provides the equations

$$n_1 \left\{ |\mathbf{n}|^2 - \frac{\alpha}{\beta} \left[T_{c,1}(p, \mathcal{B}_z) - T \right] \right\} = 0, \quad (35)$$

$$n_2 \left\{ |\mathbf{n}|^2 - \frac{\alpha}{\beta} \left[T_{c,2}(p, \mathcal{B}_z) - T \right] \right\} = 0. \quad (36)$$

The above system of equations, demonstrates that the hidden order and the antiferromagnetic states are competing and are separated by first-order line phase boundaries.

VIII. INELASTIC NEUTRON SCATTERING ENERGY GAP-MASS OF THE SPIN-0 ORBITAL ANTIFERROMAGNETIC COLLECTIVE MODE

The presence of the orbital antiferromagnetic mode with $\mathbf{Q}_{orb} = (\pm 0.4, 0, 0)$ momentum, may be recorded indirectly through the pressure and field dependence of the energy gap of the spin excitations. When the $SO(2)$ symmetry is broken, this mode acquires a mass^{10,13,14} that depends on pressure and field. This mass corresponds to the energy gap of the spin excitations. When $p = p_c$ and $\mathcal{B}_z = 0$, the $SO(2)$ symmetry emerges and the mode is massless. We may calculate the arising mass of this mode in terms of the phenomenological model of the previous section, developed for the order parameter $\mathbf{n}$. We perform a χ rotation $n_1 \rightarrow n_1 \cos \chi + n_2 \sin \chi$ and $n_2 \rightarrow n_2 \cos \chi - n_1 \sin \chi$, that yields the χ dependent free energy functional

$$\begin{aligned} \mathcal{F}(\chi) = & \left\{ \alpha \left[T - T_{c,1}(p, \mathcal{B}_z) \right] \frac{n_1^2 \cos^2 \chi + n_2^2 \sin^2 \chi + n_1 n_2 \sin 2\chi}{2} \right\} \\ & + \left\{ \alpha \left[T - T_{c,2}(p, \mathcal{B}_z) \right] \frac{n_2^2 \cos^2 \chi + n_1^2 \sin^2 \chi - n_1 n_2 \sin 2\chi}{2} \right\} + \beta \frac{|\mathbf{n}|^4}{4}. \end{aligned} \quad (37)$$

By expanding $\mathcal{F}(\chi)$ in powers of χ about its zero mean-field value, we obtain an effective free energy functional describing the static part of the orbital antiferromagnetic fluctuations. The linear term in χ , necessary disappears

$$\begin{aligned} \frac{\partial \mathcal{F}}{\partial \chi} = & \frac{\alpha}{2} \left[T - T_{c,1}(p, \mathcal{B}_z) \right] \left(-n_1^2 \sin 2\chi + n_2^2 \sin 2\chi + 2n_1 n_2 \cos 2\chi \right) \\ & + \frac{\alpha}{2} \left[T - T_{c,2}(p, \mathcal{B}_z) \right] \left(-n_2^2 \sin 2\chi + n_1^2 \sin 2\chi - 2n_1 n_2 \cos 2\chi \right) \end{aligned} \quad (38)$$

$$\left. \frac{\partial \mathcal{F}}{\partial \chi} \right|_{\chi=0} = -\alpha n_1 n_2 \left[T_{c,1}(p, \mathcal{B}_z) - T_{c,2}(p, \mathcal{B}_z) \right] = 0. \quad (39)$$

since on one hand n_1 and n_2 never coexist for $p \neq p_c$, while on the other, their temperatures become equal exactly at p_c . The second term in the expansion is associated with the mass of the collective mode.

$$\begin{aligned} \frac{\partial^2 \mathcal{F}}{\partial \chi^2} = & \alpha \left[T - T_{c,1}(p, \mathcal{B}_z) \right] \left(-n_1^2 \cos 2\chi + n_2^2 \cos 2\chi - 2n_1 n_2 \sin 2\chi \right) \\ & + \alpha \left[T - T_{c,2}(p, \mathcal{B}_z) \right] \left(-n_2^2 \cos 2\chi + n_1^2 \cos 2\chi + 2n_1 n_2 \sin 2\chi \right) \end{aligned} \quad (40)$$

$$\left. \frac{\partial^2 \mathcal{F}}{\partial \chi^2} \right|_{\chi=0} = \alpha (n_1^2 - n_2^2) \left[T_{c,1}(p, \mathcal{B}_z) - T_{c,2}(p, \mathcal{B}_z) \right] \quad (41)$$

$$\begin{aligned} = & \alpha (n_1^2 - n_2^2) \left\{ \left[T_o(0) + [T_c - T_o(0)] \frac{p}{p_c} - g_o(p) \mathcal{B}_z^2 \right] \right. \\ & \left. - \left[\frac{p_1 T_c - p_c T_a(p_1)}{p_1 - p_c} + \frac{T_a(p_1) - T_c}{p_1 - p_c} p - g_a(p) \mathcal{B}_z^2 \right] \right\}. \end{aligned} \quad (42)$$

The mass of the collective mode m is given by the following definition $\mathcal{F}_{mass} = \frac{1}{2}m^2\chi^2$. By taking the second derivative, we finally obtain

$$m^2 = \alpha (n_1^2 - n_2^2) \left\{ \frac{p_1 [T_o(0) - T_c] - p_c [T_o(0) - T_a(p_1)]}{p_1 - p_c} \left(1 - \frac{p}{p_c} \right) + [g_a(p) - g_o(p)] \mathcal{B}_z^2 \right\}. \quad (43)$$

Once again, since the order parameters n_1, n_2 never coexist, we have $n_1^2 - n_2^2 = |\mathbf{n}|^2 = n_1^2$ in the HO and $n_1^2 - n_2^2 = -|\mathbf{n}|^2 = -n_2^2$ in the LMAF. We must remark that the mass of the mode m should be related with the resonant excitation at $\mathbf{q} = \mathbf{Q}$ in the HO.

$$m^2 = \alpha |\mathbf{n}|^2 \left| \frac{p_1 [T_o(0) - T_c] - p_c [T_o(0) - T_a(p_1)]}{p_1 - p_c} \left(1 - \frac{p}{p_c} \right) + [g_a(p) - g_o(p)] \mathcal{B}_z^2 \right|. \quad (44)$$

The contribution of the kinetic energy of the mode to the free energy functional, is expressed as $-\frac{1}{2}\rho\omega_{\mathbf{q}}^2\chi^2$. ρ is a coefficient that would arise if we had calculated the fluctuating part of the collective mode. Such a treatment would demand a microscopic model that could properly take into account the main Fermi surface sheets of this compound. This coefficient is defined in meV and shall be considered constant. The fact that we do not exactly know this parameter, prevents us from obtaining the exact energy gap. However, we may infer the normalized field and temperature dependence of the energy gap of a spin excitation carrying momentum $\mathbf{q}$, defined as $\omega_{\mathbf{q}}^0(T, p, \mathcal{B}_z)/\omega_{\mathbf{q}}^0(T, p, 0)$ and $\omega_{\mathbf{q}}^0(T, p, \mathcal{B}_z)/\omega_{\mathbf{q}}^0(0, p, \mathcal{B}_z)$, respectively.

$$\frac{\omega_{\mathbf{q}}^0(T, p, \mathcal{B}_z)}{\omega_{\mathbf{q}}^0(T, p, 0)} = \left| \frac{\mathbf{n}(T, p, \mathcal{B}_z)}{\mathbf{n}(T, p, 0)} \right| \sqrt{1 + \frac{p_c (p_1 - p_c) [g_a(p) - g_o(p)]}{(p_c - p) \left\{ p_1 [T_o(0) - T_c] - p_c [T_o(0) - T_a(p_1)] \right\}} \mathcal{B}_z^2}, \quad p \neq p_c. \quad (45)$$

In order to continue, we use a number of experimental data so to identify the HO and LMAF critical temperatures and magnetic couplings. The specific pressure dependence that we have considered for the critical temperatures, will give a phase boundary that has a vertical line in the $p - \mathcal{B}$ phase diagram. However, experimental evidence¹¹ show that the first-order phase boundary is a straight line only for temperatures below $\sim 8\text{K}$. In this case $p_c = 0.5\text{GPa}$, $T_c \simeq 17.8\text{K}$ ¹¹. This choice of p_c , restricts the validity of our phenomenological theory to low temperatures. However, the neutron scattering measurements are usually performed below 8K. Consequently, our model works well in this region and we may compare our calculations to the experimental data. Specifically we use: $T_o(0\text{GPa}) = 17.5\text{K}$ at $\mathcal{B}_z = 0$ ^{15,16}, $p_1 = 2\text{GPa}$, $T_a(p_1) = 19.5\text{K}$ at $\mathcal{B}_z = 0$ ¹¹, $\mathcal{B}_z^{crit,o}(0\text{GPa}) \simeq 40\text{T}$ at $T = 0\text{K}$ ^{15,16} and that $\mathcal{B}_z^{crit,o}(0.72\text{GPa}) = 15\text{T}$ at $T \simeq 16\text{K}$ ¹². Moreover, we have used the experimentally extracted dependence $\omega_{\mathbf{Q}}^0(2\text{K}, 0\text{GPa}, \mathcal{B}_z)/\omega_{\mathbf{Q}}^0(2\text{K}, 0\text{GPa}, 0\text{T}) = \sqrt{1 + 0.005 \cdot \mathcal{B}_z^2}$ ¹⁷, for the $\mathbf{Q} = (1, 0, 0)$ resonance in the HO. Finally, from Ref.¹², we have used that for pressure $p = 1.1\text{GPa}$ and temperature $T=0\text{K}$, the LMAF state undergoes a first-order transition to the HO state for $\mathcal{B}_z = 12\text{T}$. At this critical point of the phase diagram, the orbital antiferromagnetic collective mode becomes massless, providing zero energy gap to the spin excitation spectrum. The arising condition from this experimental feedback may interpreted as $\omega_{\mathbf{Q}}^0(0\text{K}, 1.1\text{GPa}, 12\text{T}) = 0$. The aforementioned conditions define in a unique manner the parameters of our theory providing the dependences: $T_o(p) = 17.5 + 0.6p(\text{K})$, $T_a(p) = 17.2 + 1.13p(\text{K})$, $g_o(p) = 0.011 - 0.003p(\text{K}/\text{T}^2)$ and $g_a(p) = 0.012 - 0.019p(\text{K}/\text{T}^2)$. The normalized magnetic-field-dependence of the energy spectrum reads

$$\frac{\omega_{\mathbf{q}}^0(T, p, \mathcal{B}_z)}{\omega_{\mathbf{q}}^0(T, p, 0)} = \left| \frac{\mathbf{n}(T, p, \mathcal{B}_z)}{\mathbf{n}(T, p, 0)} \right| \sqrt{1 + \frac{25 + 12p}{0.5 - p} (0.01\mathcal{B}_z)^2}, \quad p \neq p_c. \quad (46)$$

Finally, for the two resonances we have:

$$\frac{\omega_{\mathbf{Q}}^0(T, p, \mathcal{B}_z)}{\omega_{\mathbf{Q}}^0(T, p, 0)} = \sqrt{1 - \frac{0.011 - 0.003p}{17.5 + 0.6p - T} \mathcal{B}_z^2} \sqrt{1 + \frac{25 + 12p}{0.5 - p} (0.01\mathcal{B}_z)^2}, \quad T < 8\text{K} \text{ (HO)}, \quad (47)$$

$$\frac{\omega_{\mathbf{Q}_1}^0(T, p, \mathcal{B}_z)}{\omega_{\mathbf{Q}_1}^0(T, p, 0)} = \sqrt{1 - \frac{0.012 - 0.0019p}{17.2 + 1.13p - T} \mathcal{B}_z^2} \sqrt{1 + \frac{25 + 12p}{0.5 - p} (0.01\mathcal{B}_z)^2}, \quad T < 8\text{K} \text{ (LMAF)}. \quad (48)$$

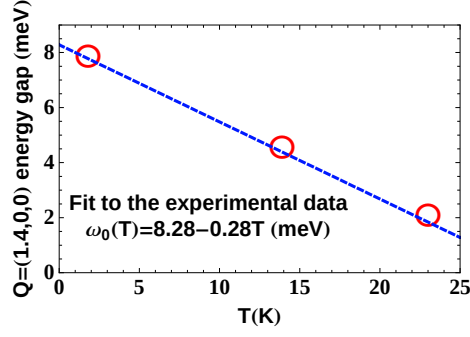


FIG. 4: Interpolation of experimental data taken from¹¹, concerning the temperature dependence of the energy gap of the Q_1 spin excitation, observed in the large antiferromagnetic state.

We have obtained the $p - \mathcal{B}$ phase diagram at $T=0K$, by retrieving all the combinations of pressure and field that reduce the above expressions to zero. These values have provided the first-order boundary of the HO and the LMAF and the transition from the HO to a polarized paramagnetic metal (PPM). In addition, we used Eq.47, to compare the theoretical outcome for $\omega_Q^0(T, 0GPa, \mathcal{B}_z)/\omega_Q^0(T, 0GPa, 0)$ with the corresponding experimental values¹⁷.

The normalized temperature dependence of the spin excitation energy gap becomes

$$\frac{\omega_Q^0(T, p, \mathcal{B}_z)}{\omega_Q^0(0, p, \mathcal{B}_z)} = \sqrt{\left|1 - \frac{T}{17.5 + 0.6p - (0.011 - 0.003p)\mathcal{B}_z^2}\right|}, \quad T < 8K \text{ (HO)}, \quad (49)$$

$$\frac{\omega_{Q_1}^0(T, p, \mathcal{B}_z)}{\omega_{Q_1}^0(0, p, \mathcal{B}_z)} = \sqrt{\left|1 - \frac{T}{17.2 + 1.13p - (0.012 - 0.0019p)\mathcal{B}_z^2}\right|}, \quad T < 8K \text{ (LMAF)}. \quad (50)$$

We observe that in this case all the parameters are fixed. The conditions that we have used to define the values of these parameters were uncorrelated to any information concerning the temperature dependence of the energy gap of any of the possible resonances. Any theoretical calculation concerning the temperature dependence will constitute a prediction of the $SO(2)$ theory.

We go on with proposing an explanation for the observed Q_1 resonance in the LMAF state. The spin-0 orbital antiferromagnetic mode cannot couple to a Q_1 modulated external field, $\mathcal{B}_z^{Q_1}$, even in the presence of the LMAF. The reason is its $d_{x^2-y^2}$ momentum structure. However, a resonant excitation is possible to arise in the case of an anisotropic s-wave order parameter for the LMAF, that could provide appropriate coherence factors for the formation of a spin-exciton at Q_1 . In order to test this possibility, we have made a comparison to experimental measurements. For this task, we have used the data presented in Fig.4, that were taken from Ref.¹¹ and concern the temperature dependence of the energy gap of this mode. Since, there were not many available data below $T=8K$, which is the limit of the validity of our theory, we have interpolated the experimental data. We have compared the interpolated data $\omega_0(T)/\omega_0(0) = (8.28 - 0.28T)/8.28$ to the normalized energy gap of Eq.50. The theoretical and the experimental curves are in very good agreement indicating that the normalized energy gap of the resonance mode scales with $|\mathbf{n}(T, p, 0)|/|\mathbf{n}(0, p, 0)|$. This clearly implies that the spin excitation develops a gap proportional to the LMAF order parameter, supporting our proposal.

IX. POLAR KERR EFFECT

The Kerr angle¹⁹⁻²¹ is defined as

$$\vartheta_K = \frac{4\pi}{n(n^2 - 1)da^2} \frac{\sigma_{xy}^{\Im}(\omega)}{\omega}, \quad (51)$$

where n is the refractive index, d is the c-axis thickness of the sample, $a = 5\text{\AA}$ the in plane lattice constant and $\sigma_{xy}^{\Im}$ the imaginary part of the dynamic Hall conductivity. In the low field regime ($\mathcal{B} \leq 20T$), the dynamic Hall conductivity is dominated by the topological contribution. For a Sagnac inteferometer¹⁹ $\hbar\omega = 0.8eV = 6420\text{cm}^{-1}$

and $\lambda = 1550\text{nm}$, while the plasma frequency of URu_2Si_2 is $\hbar\omega_p = 2131\text{cm}^{-1} \simeq 266\text{meV}^{22}$. The refractive index in this case is defined as $n = \sqrt{1 - (\omega_p/\omega)^2}$. Since $\omega \gg \omega_p$ we may use the approximation $n \simeq 1$ and $n^2 - 1 = -(\omega_p/\omega)^2$.

For the calculations of the Polar Kerr effect in the presence of small external static magnetic fields, only the topological dynamic Hall conductivity is important in our case, defined as

$$\sigma_{xy}(\omega) = \frac{\Pi_{cc}^{xy}(\mathbf{q} \rightarrow 0, i\omega_s \rightarrow \omega + i0^+)}{-i\omega} \quad (52)$$

with $\Pi_{xy}^{cc}(\mathbf{q}, i\omega_s)$ the current-current charge polarization function originating from the bubble diagram

$$\Pi_{ij}^{cc}(i\omega_s, \mathbf{q}) = \frac{a^2}{\beta} \sum_{i\mathbf{k}_n, \mathbf{k}} Tr_{\tau, \sigma} \left\{ \hat{\mathcal{G}}(ik_n, \mathbf{k}) \hat{\Gamma}_i^\mu(\mathbf{k}, \mathbf{k} + \mathbf{q}) \tau_\mu \hat{\mathcal{G}}(ik_n + i\omega_s, \mathbf{k} + \mathbf{q}) \hat{\Gamma}_j^\nu(\mathbf{k} + \mathbf{q}, \mathbf{k}) \tau_\nu \right\} \quad (53)$$

and $\hat{\mathcal{G}}(ik_n, \mathbf{k})$ is the bare matrix Matsubara Green's function

$$\begin{aligned} \hat{\mathcal{G}}(ik_n, \mathbf{k}) &= \frac{1}{ik_n - \mu_B \sigma_3 - m_z(\mathbf{k}) - \mu - \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\tau}} = \frac{ik_n - \mu_B \sigma_3 - m_z(\mathbf{k}) - \mu + \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\tau}}{(ik_n - \mu_B \sigma_3 - m_z(\mathbf{k}) - \mu)^2 - E^2(\mathbf{k})} \\ &= \frac{1}{2E(\mathbf{k})} \left\{ \frac{E(\mathbf{k}) + \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\tau}}{ik_n - \mu_B \sigma_3 - m_z(\mathbf{k}) - \mu - E(\mathbf{k})} + \frac{E(\mathbf{k}) - \hat{\mathbf{g}}(\mathbf{k}) \cdot \boldsymbol{\tau}}{ik_n - \mu_B \sigma_3 - m_z(\mathbf{k}) - \mu + E(\mathbf{k})} \right\} \end{aligned} \quad (54)$$

and the vertex functions $\hat{\Gamma}_i^\mu(\mathbf{k}, \mathbf{k} + \mathbf{q})$ are defined as the coefficients of the fermion-gauge field coupling written in the form $\sum_{\mathbf{q}} J_i^c(\mathbf{q}) A^i(-\mathbf{q}) = \sum_{\mathbf{q}, \mathbf{k}} \Psi_{\mathbf{k}+\mathbf{q}}^\dagger \hat{\Gamma}_i^\mu(\mathbf{k} + \mathbf{q}, \mathbf{k}) \tau_\mu \Psi_{\mathbf{k}} A^i(-\mathbf{q})$. Consequently they are known if we find the fermionic currents. We start by the equation of continuity of the electric charge $Q_{el} = \int d\mathbf{r} \rho(\mathbf{r})$ in momentum space $\dot{\rho}(\mathbf{q}) - i\mathbf{q} \cdot \mathbf{J}^c(\mathbf{q}) = 0$, where we have introduced the electric charge density $\rho(\mathbf{q}) = -e \sum_{\mathbf{k}} \Psi_{\mathbf{k}+\mathbf{q}}^\dagger \Psi_{\mathbf{k}}$. The corresponding electric current can be derived from the equation of continuity as the limit

$$\mathbf{J}^c(\mathbf{q}) = -i \lim_{\mathbf{q} \rightarrow 0} \nabla_{\mathbf{q}} \dot{\rho}(\mathbf{q}) = \lim_{\mathbf{q} \rightarrow 0} \nabla_{\mathbf{q}} [\mathcal{H}, \rho(\mathbf{q})] = -e \sum_{\mathbf{k}} \Psi_{\mathbf{k}+\mathbf{q}}^\dagger \hat{\mathbf{V}}(\mathbf{k}) \Psi_{\mathbf{k}} \quad (55)$$

with $\hat{\mathbf{V}}(\mathbf{k}) = \nabla_{\mathbf{k}} \hat{\mathcal{H}}(\mathbf{k})$ the velocity defined in spinor space. Consequently $\hat{\Gamma}_i^0(\mathbf{k} + \mathbf{q}, \mathbf{k}) = 0$ and $\hat{\Gamma}_i^{\alpha}(\mathbf{k} + \mathbf{q}, \mathbf{k}) = \frac{\partial \hat{\mathbf{g}}(\mathbf{k})}{\partial k_i}$. Straightforward calculation of the polarization tensor yields the Hall topological conductivity

$$\sigma_{xy}(\omega) = \frac{e^2}{\hbar v} \sum_{\mathbf{k}, s, \nu} \frac{4E^2(\mathbf{k}) n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] \Omega_{s,\nu}^z(\mathbf{k})}{[\hbar\omega + i\eta - 2E(\mathbf{k})] [\hbar\omega + i\eta + 2E(\mathbf{k})]}.$$

For $\omega > 0$ the Hall conductivity has a contribution from only the first pole and one may write

$$\sigma_{xy}(\omega) = \frac{e^2}{\hbar v} \sum_{\mathbf{k}, s, \nu} \frac{4E^2(\mathbf{k}) n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] \Omega_{s,\nu}^z(\mathbf{k})}{\hbar\omega + i\eta + 2E(\mathbf{k})} \left\{ \frac{\mathcal{P}}{\hbar\omega - 2E(\mathbf{k})} - i\pi\delta[\hbar\omega - 2E(\mathbf{k})] \right\} \quad (56)$$

where $\mathcal{P}$ denotes the principal value of the sum. The imaginary part of the conductivity is given as

$$\sigma_{xy}^{\Im}(\omega) = -\frac{\pi e^2 \hbar \omega}{2\hbar v} \sum_{\mathbf{k}, s, \nu} n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] \Omega_{s,\nu}^z(\mathbf{k}) \delta[\hbar\omega - 2E(\mathbf{k})].$$

where due to the delta function we have the simplification $E_{s,\nu}^{\mathcal{B}}(\mathbf{k}) = -\mu - [\mu_B s + m_z(\mathbf{k})]\mathcal{B} + \nu\hbar\omega/2$. Typically, $\hbar\omega$ is of the order of eV, definitely larger than the energy scales considered here. This means that $n_F[E_{s,\nu}^{\mathcal{B}}(\mathbf{k})] \simeq n_F[\nu\hbar\omega/2]$. For low fields, the physics may be well described by considering an expansion around the $\mathbf{k}_0 = (\frac{\pi}{2}, \frac{\pi}{2})$ point. In this

case, $\Omega_{s,\nu}^z(\mathbf{k}) \simeq 2\nu a^2 t \Delta_1 \Delta_2 / E^3(\mathbf{k}) = 16\nu a^2 t \Delta_1 \Delta_2 / (\hbar\omega)^3$, $E(\mathbf{k}) = \sqrt{\Delta_1^2 + \Delta_2^2 (\delta k_x - \delta k_y)^2 + (2t)^2 (\delta k_x + \delta k_y)^2}$, with $\delta \mathbf{k} = \mathbf{k} - \mathbf{k}_0$ and $\frac{1}{v} \sum_{\mathbf{k} \in \mathcal{B.Z.}} = \int_{\Delta_1}^{E_c} dE E / [2\pi(4t\Delta_2)]$.

$$\sigma_{xy}^{\mathfrak{S}}(\omega) = \frac{e^2 \Delta_1}{\hbar} \frac{1 - 2n_F(\hbar\omega/2)}{\hbar\omega} a^2 \simeq \frac{e^2}{\hbar} \frac{\Delta_1}{\hbar\omega} a^2 \quad (57)$$

The Kerr angle is equal to

$$\vartheta_K(\mathcal{B}, T) = \frac{4\pi}{n(n^2 - 1)da^2} \frac{\sigma_{xy}^{\mathfrak{S}}(\omega)}{\omega} \simeq -\frac{2}{n(n^2 - 1)} \frac{e^2}{\hbar} \frac{\lambda}{d} \frac{\Delta_1(\mathcal{B}, T)}{\hbar\omega} \quad (58)$$

$$\vartheta_K(\mathcal{B}, T) \simeq -2 \frac{e^2}{\hbar c} \frac{\lambda}{d} \frac{\Delta_1(\mathcal{B}, T)}{\hbar\omega_p} \left(\frac{\omega}{\omega_p} \right),$$

By taking into account the value of the fine structure constant $e^2/\hbar c = 1/137$ and by setting $d \simeq 2\text{nm}$, we obtain a rough estimation of the Kerr angle as $\vartheta_K \simeq 128\Delta_1\text{mrad}$ with Δ_1 in meV. The maximum value of Δ_1 is equal to 1.5meV, which defines an upper bound $\vartheta_K \leq 190\text{mrad}$.

* Electronic address: pkotetes@central.ntua.gr

- ¹ Elgazzar S. *et al.* Hidden order in URu₂Si₂ originates from Fermi surface gapping induced by dynamic symmetry breaking. *Nature Materials* **8**, 337 (2009).
- ² Wohlfarth E. P. and Rhodes P. Collective Electron Metamagnetism. *Philos. Mag.* **7**, 1817 (1962).
- ³ Xiao D., Chang M.-C., and Niu Q. Berry Phase Effects on Electronic Properties. arXiv:0907.2021.
- ⁴ Zhang C., Tewari S., Yakovenko V. M., and Das Sarma S. Anomalous Nernst effect from a chiral d-density-wave state in underdoped cuprate superconductors. *Phys. Rev. B* **78**, 174508 (2008).
- ⁵ Kotetes P., and Varelogiannis G. Magnetic-field-induced chiral particle-hole condensates. *Phys. Rev. B* **80**, 212401 (2009).
- ⁶ Kotetes P., and Varelogiannis G. Chirality Induced Tilted-Hill Giant Nernst Signal. arXiv:0911.2512.
- ⁷ Goswami P. Fermi surface topology and magneto-quantum oscillations for under-doped YBCO with hopping anisotropy. arXiv:0910.3464.
- ⁸ Behnia K., Measson M.-A., Kopelevich Y. Nernst effect in semi-metals: the meritorious heaviness of electrons. *Phys. Rev. Lett.* **98**, 076603 (2007).
- ⁹ Zhu J.-X., and Balatsky A. V. Field induced $d_{x^2-y^2} + id_{xy}$ state in d-density-wave metals. *Phys. Rev. B* **65**, 132502 (2002).
- ¹⁰ Demler E., Hanke W., and Zhang S.-C. SO(5) theory of antiferromagnetism and superconductivity. *Rev. Mod. Phys.* **76**, 909 (2004).
- ¹¹ Villaume A. *et al.* Signature of hidden order in heavy fermion superconductor URu₂Si₂: Resonance at the wave vector $Q_0=(1,0,0)$. *Phys. Rev. B* **78**, 012504 (2008).
- ¹² Aoki D. *et al.* Field Reentrance of the Hidden Order State of URu₂Si₂ under Pressure. *J. Phys. Soc. Jpn.* **78**, 053701 (2009).
- ¹³ Haule K., and Kotliar G. Arrested Kondo effect and hidden order in URu₂Si₂. *Nature Physics* **5**, 796 (2009).
- ¹⁴ Haule K., and Kotliar G. Complex Landau Ginzburg Theory of the Hidden Order in URu₂Si₂. arXiv:0907.3892.
- ¹⁵ Harrison N., Jaime M., and Mydosh J. A. Reentrant Hidden Order at a Metamagnetic Quantum Critical End Point. *Phys. Rev. Lett.* **90**, 096402 (2003).
- ¹⁶ Kim K. H. *et al.* Magnetic-Field-Induced Quantum Critical Point and Competing Order Parameters in URu₂Si₂. *Phys. Rev. Lett.* **91**, 256401 (2003).
- ¹⁷ Bourdarot F., Fak B., Habicht K., and Prokes K. Inflection point in the Magnetic Field Dependence of the Ordered Moment of URu₂Si₂ Observed by Neutron Scattering in Fields up to 17 T. *Phys. Rev. Lett.* **90**, 067203 (2003).
- ¹⁸ Demler E., Kohno H., and Zhang S.-C. π excitation of the t-J model. *Phys. Rev. B* **58**, 5719 (1998).
- ¹⁹ Kapitulnik A. *et al.* Polar Kerr Effect as Probe for Time-Reversal Symmetry Breaking in Unconventional Superconductors. *New J. Phys.* **11**, 055060 (2009).
- ²⁰ Tewari S., Zhang C., Yakovenko V. M., and Das Sarma S. Time-Reversal Symmetry Breaking by a (d+id) Density-Wave State in Underdoped Cuprate Superconductors. *Phys. Rev. Lett.* **100**, 217004 (2008).
- ²¹ Mineev V. P. Broken time-reversal symmetry in the superconducting state of Sr₂RuO₄. *Phys. Rev. B* **76**, 212501 (2007).
- ²² Degiorgi L. *et al.* The electrodynamic response of heavy-electron materials with magnetic phase transitions. *Z. Phys. B* **102**, 367 (1997).